

## **EFFECT OF NANO Cr<sub>2</sub>O<sub>3</sub> ADDITION ON (Bi-Pb)-Sr-Ca-Cu-O SUPERCONDUCTOR**

Kong Wei and Roslan Abdul Shukor

*School of Applied Physics, Universiti Kebangsaan Malaysia*  
*43600 Bangi, Selangor, Malaysia*

### **ABSTRACT**

The effect of nano Cr<sub>2</sub>O<sub>3</sub> addition on (B, Pb)-Sr-Ca-Cu-O superconductor has been studied. The samples were prepared from the co-precipitation method in the bulk form. Both the critical temperature ( $T_c$ ) and critical current density ( $J_c$ ) were determined by the four point-probe technique. Phases analyses of the samples by XRD, microstructures determination by SEM and distribution of nano Cr<sub>2</sub>O<sub>3</sub> by EDAX have been carried out. The maximum  $T_c$  and  $J_c$  were observed for 0.1 wt% nano Cr<sub>2</sub>O<sub>3</sub> in the initial sample. The increase in the  $J_c$  of all the samples can be explained due to the effective flux pinning of nano Cr<sub>2</sub>O<sub>3</sub> to the samples.

### **INTRODUCTION**

Multi-phase superconductor system Bi-Sr-Ca-Cu-O was discovered by Maeda *et al.* in 1988 [1]. It was found that a small amount of CrO<sub>3</sub> doping improves the flux pinning, with the effective pinning center due to Cr substitution for Cu, while excessive Cr-ion doping degrades the superconductivity of Bi<sub>1.6</sub>Pb<sub>0.4</sub>Sr<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>10</sub> (2223) [2].  $T_c$  of the Cr-doped Bi-Sr-Ca-Cu-O decreased due to the decrease of the hole concentration through substitution of Cr<sup>3+</sup> for Cu<sup>2+</sup>. The substitution also causes appreciable change in the normal state conductivity [3]. At 77 K, self-field  $J_c$  of the Nd-added samples are found much better than undoped one [4]. To the best of our knowledge, nano Cr<sub>2</sub>O<sub>3</sub> addition on Bi-Sr-Ca-Cu-O superconductors have not been reported earlier. In this paper, we report on the effect of nano Cr<sub>2</sub>O<sub>3</sub> addition in Bi-Sr-Ca-Cu-O on the critical temperature ( $T_c$ ), the critical current density ( $J_c$ ) at 77 K and the phase variations. The distribution of nano Cr<sub>2</sub>O<sub>3</sub> in the samples is also presented.

### **METHODOLOGY**

The samples were prepared from ultrafine superconductor powders developed from the co-precipitation method. Nano Cr<sub>2</sub>O<sub>3</sub> (about 100 nm) with the amount of 0.1 wt%, 0.3 wt%, 0.5 wt%, 0.7 wt% and 1.0 wt% were added to the powder. Samples were pressed into pellets of 13 mm diameter and 2 mm thickness and sintered at 850 °C for 48 hours. The electrical resistance-temperature measurements were carried out by the four point-probe technique in conjunction with a CTI cryogenics closed cycle refrigerator Model 22. The critical current density was measured on bar-shape sample at 77 K. The critical current density was determined using the 1  $\mu$ V/cm criterion. Powder X-ray diffraction

measurement was performed using a Siemens D 5000 diffractometer with  $\text{CuK}_\alpha$  radiation. The volume fraction of the 2223 phase and  $(\text{Bi}_{1.6}\text{Pb}_{0.4})\text{Sr}_2\text{CaCu}_2\text{O}_8$  (2212) phase was estimated by assuming that the amounts of those phases are proportional to the strongest diffraction line of each phase. Microstructures were determined from scanning electron micrographs (SEM). The distribution of nano  $\text{Cr}_2\text{O}_3$  was investigated through the Energy Dispersive X-Ray Analysis (EDAX).

## RESULTS AND DISCUSSION

$T_{c\text{-onset}}$ ,  $T_{c\text{-zero}}$ ,  $J_c$  at 77 K, percentage of the 2223 and 2212 phase and distribution of nano  $\text{Cr}_2\text{O}_3$  are shown in Table 1. Figure 1 shows the electrical resistance versus temperature curve for the samples. The result shows that  $T_{c\text{-onset}}$  for the 0.1 wt% nano  $\text{Cr}_2\text{O}_3$  is the highest, which is 111 K whereas the non-added sample show  $T_{c\text{-onset}}$  of 108 K. When nano  $\text{Cr}_2\text{O}_3$  addition is increased from 0.3 wt% to 1.0 wt%, we found that  $T_{c\text{-onset}}$  has decreased from 110 K to 100 K whereas  $T_{c\text{-zero}}$  has decreased from 97 K to 81 K.

Table 1:  $T_{c\text{-onset}}$ ,  $T_{c\text{-zero}}$ ,  $J_c$  at 77 K, percentage of phase 2223 and 2212 and distribution of nano  $\text{Cr}_2\text{O}_3$ .

$x$ (wt%)	$T_{c\text{-onset}}$ ( $\pm 1$ K)	$T_{c\text{-zero}}$ ( $\pm 1$ K)	$J_c$ at 77 K (mA/cm <sup>2</sup> )	Volume Fraction (%)		Distribution of Nano $\text{Cr}_2\text{O}_3$ (count/ $\mu\text{m}^2$ )
				2223 (%)	2212 (%)	
0	108	98	0.03	62	38	-
0.1	111	101	3980	71	29	0.09
0.3	110	97	592	69	31	-
0.5	108	97	393	68	32	0.29
0.7	105	88	14	68	32	-
1.0	100	81	-	67	33	0.57

Further addition of nano  $\text{Cr}_2\text{O}_3$  up to 1.0 wt% decrease both  $T_{c\text{-onset}}$  and  $T_{c\text{-zero}}$  of the samples. The decrease of the critical temperature is caused by the over-doping of nano  $\text{Cr}_2\text{O}_3$  to the Bi2223 system. Barik *et al.* (2000) reported the suppression of  $T_c$  with increase of Cr concentration supports the pair-breaking mechanism. Hu *et al.* (2001) has reported that a small amount of  $\text{CrO}_3$  doping improves the flux pinning, with the effective pinning center due to Cr substitution for Cu, while excessive Cr-ion doping degrades the superconductivity of Bi2223.

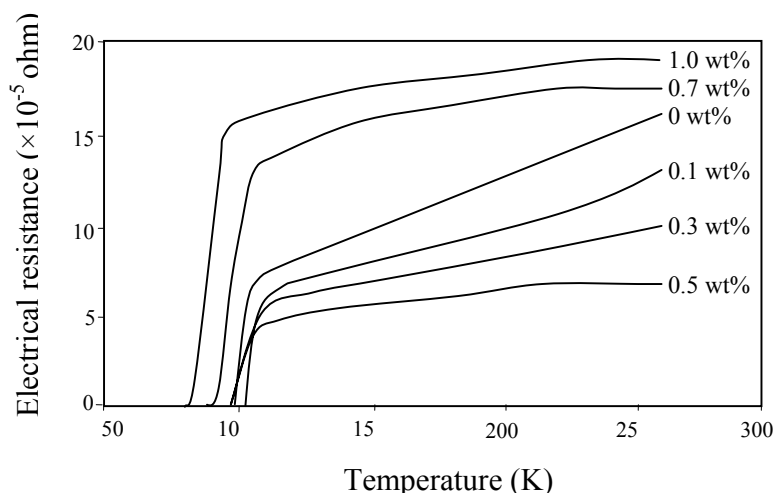


Figure 1: Electrical resistance versus temperature curve.

For the non added sample, the  $J_c$  at 77 K is about  $0.03 \text{ mA/cm}^2$ .  $J_c$  of the sample has been increased to  $3980 \text{ mA/cm}^2$  while 0.1 wt% nano  $\text{Cr}_2\text{O}_3$  addition is applied.  $J_c$  starts to decrease when the higher amounts of nano  $\text{Cr}_2\text{O}_3$  are added. There is an increase in  $J_c$  for the all the nano  $\text{Cr}_2\text{O}_3$ -added samples compared to the non-added sample. In other words, the flux pinning strength of the added samples is significantly enhanced compared to the non-added sample. Meanwhile, the presence of nano  $\text{Cr}_2\text{O}_3$  in the Bi2223 samples, has acted as an effective flux pinning centres.

Figure 2 shows the XRD patterns of the samples. The main peaks can be identified as (020). These samples do not show single phase because it has been found that there are a few peaks which show the phase of 2212. Volume fraction can be calculated from the X-ray intensity of the (020) peaks of Bi2223 and the (\*) peaks of Bi2212. The volume fraction of 2223 phase for sample with the addition of 0.1 wt% nano  $\text{Cr}_2\text{O}_3$  shows the highest percentage, which is 71%. However, there is not much difference in the volume fraction when further addition of nano  $\text{Cr}_2\text{O}_3$  is applied. The results show that a small amount of nano  $\text{Cr}_2\text{O}_3$  has no influence on the Bi2223 system. From the result, it shows that the highest percentage of 2223 phase may give the highest critical temperature.

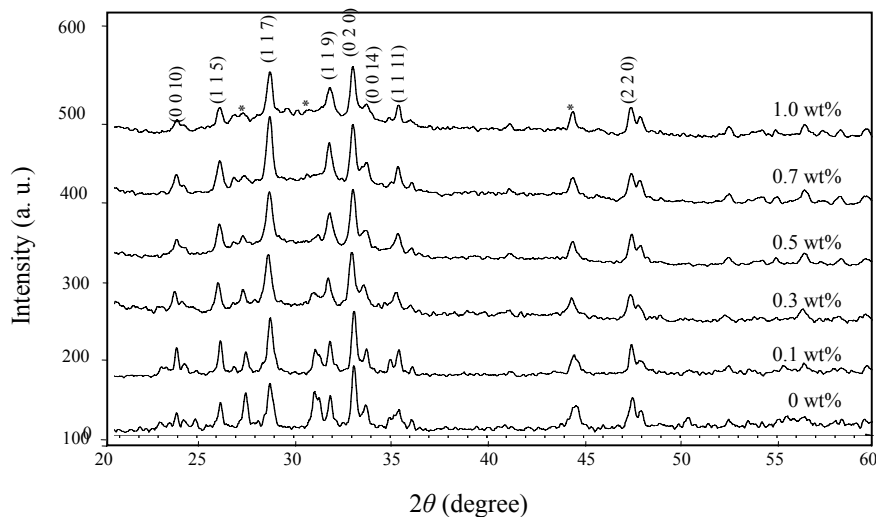


Figure 2: XRD patterns of the non-added and nano  $\text{Cr}_2\text{O}_3$ -added samples; (\*) denotes the Bi2212 phase.

Figure 3 shows the SEM micrograph for samples with addition of 0.1 wt%, 0.5 wt% and 1.0 wt% nano  $\text{Cr}_2\text{O}_3$ . All of the samples show the similar grain alignment. Meanwhile, the adding amount is very small and does not change the grain size and alignment. The distribution of  $\text{Cr}_2\text{O}_3$  is showed by the red spots. The distribution of nano  $\text{Cr}_2\text{O}_3$  increases from 0.09  $\text{count}/\mu\text{m}^2$  for sample 0.1 wt%, to 0.57  $\text{count}/\mu\text{m}^2$  for sample 1.0 wt%.

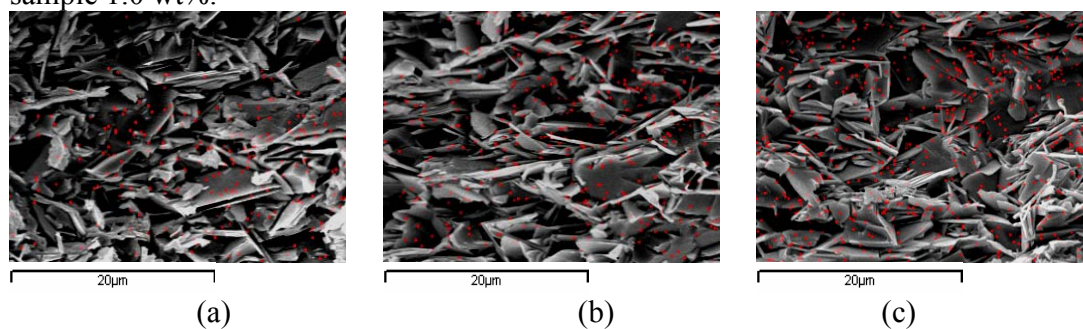


Figure 3: SEM micrographs of samples (a) 0.1 wt%, (b) 0.5 wt% and (c) 1.0 wt%.

## CONCLUSION

Nano Cr<sub>2</sub>O<sub>3</sub> additions on Bi-Sr-Ca-Cu-O can improve the superconducting properties of the samples. Sample with the addition of 0.1 wt% has the highest  $T_{c-onset}$  and  $T_{c-zero}$ . The same sample also shows the highest volume fraction of 2223 phase which is 71%. The results show that an appropriate amount of nano Cr<sub>2</sub>O<sub>3</sub> can improve the superconducting properties of the Bi-based samples, while excessive nano Cr<sub>2</sub>O<sub>3</sub> addition leads to the degradation of superconductivity of Bi2223.  $J_c$  of all the samples has been increased with addition of nano Cr<sub>2</sub>O<sub>3</sub>. Nano Cr<sub>2</sub>O<sub>3</sub> addition in very small percentage in (Bi, Pb)-2223 will enhance the critical current density effectively.

## REFERENCES

- [1] Maeda, H., Tanaka, Y., Fukotomi, M. & Asuno, T. (1988); A new high  $T_c$  oxide superconductor without a rare earth element, *Jap. J. of Appl. Phys.*, **27**, L127-L130.
- [2] Hu, T., Xiao, H., Pu, M.H., Wu, X.C., Song, W.H., Zhao, B., Sun, Y.P. & Du, J.J. (2001); Improved  $J_c$  behavior under magnetic field in Bi<sub>1.8</sub>Pb<sub>0.4</sub>Sr<sub>2</sub>Ca<sub>2.2</sub>Cu<sub>3-x</sub>Cr<sub>x</sub>O<sub>y</sub>/Ag tapes, *Solid State Phys.*, **186**, 135-141.
- [3] Barik, H.K., Ghorai, S.K., Bhattacharya, S., Kilian, D. & Chaudhuri, B.K., (2000); Effect of Cr doping on the electrical conductivity and Seebeck Coefficient in the superconductors obtained for the Bi-Pb-Sr-Ca-Cu-Cr-O-type glassy precursors by annealing, *J. of Mater. Res.*, **15**, 1076-1082.
- [4] Aloysius, R.P., Guruswamy, P. & Syamaprasad, U. (2005); Enhanced flux pinning in (Bi, Pb)-2223 superconductor by Nd addition, *Supercond. Sci. Technol.*, **18**, 427-431.